

AVAILABLE IN AUSTRALIA ONLY

18.1 GENERAL INFORMATION

PERFORMANCE RELATED	INSTALLATION RELATED

Product

ChemSet™ 801 is a heavy duty Vinyl Ester anchoring adhesive.

Benefits, Advantages and Features

Suitable for structural applications:

- High bond strength

Suitable for use in contact with drinking water:

- Meets AS/NZ4020 - 1999

Suitable for diamond cored holes:

- High bond strength

Versatile


- Suitable for cold and temperate climates
- VOC Compliant

High Productivity

- Fast Cure
- Easy cold weather dispensing

Australian Made

Installation

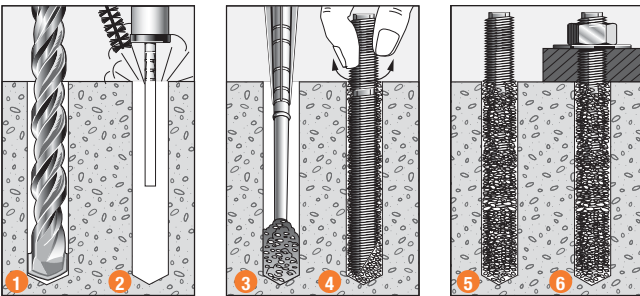

1. Drill recommended diameter and depth hole.
2. **Important:** Use Ramset™ Dustless Drilling System to ensure holes are clean. Alternatively, clean dust and debris from hole with stiff wire or nylon brush and blower in the following sequence: blow x 4, brush x 3, blow x 4, brush x 3, blow x 4.
3. Insert mixing nozzle to bottom of hole. Fill hole to 3/4 the hole depth slowly, ensuring no air pockets form.
4. Insert Ramset™ ChemSet™ Anchor Stud/rebar to bottom of hole while turning.
5. ChemSet™ Injection to cure as per setting times.
6. Attach fixture.



Principal Applications

- Structural steel
- Starter bars
- Handrails
- Timber frames in domestic housing

Installation temperature limits:

- Substrate: 0°C to 40°C.
- Adhesive: 5°C to 40°C.

Load should not be applied to anchor until the chemical has sufficiently cured as specified.

Service temperature limits:

-40°C to 80°C.

Setting Times

Substrate Temperature	801	
	Gel Time (mins)	Loading Time (mins)
40°C	–	–
30°C	4	35
25°C	5	40
20°C	6	50
10°C	10	85
5°C	18	145

Note: Cartridge temperature minimum 5°C.

AVAILABLE IN AUSTRALIA ONLY

**Installation and performance details:
ChemSet™ Injection 801 and Reinforcing Bar**

Chemical Anchoring - Reinforcing Bar Anchorage

Anchor Size, d_b (mm)	Drilled Hole diam., d_h (mm)	Anchor Effective Depth, h (mm)	Optimum dimensions*			Reduced Characteristic Capacity #				
			Edge* distance, e_c (mm)	Anchor spacing, a_c (mm)	Concrete substrate thickness, b_m (mm)	Gr 500 Rebar - Steel		Concrete**		
						Tension, ϕN_{us} (kN)***	Shear, ϕV_{us} (kN)	Tension, ϕN_{uc} (kN)		
								20 MPa	32 MPa	40 MPa
10	14	90	40	60	115	31.4	21.4	9.2	11.6	13.0
12	16	110	50	70	140	45.2	30.8	13.5	17.0	19.0
16	20	125	65	100	160	80.4	54.8	20.4	25.8	28.9
20	25	150	80	120	190	125.6	85.7	30.6	38.7	43.3
		170			215			34.7	43.9	49.0
24	30	180	100	145	240	180.8	123.3	44.1	55.7	62.3
		210			270			51.4	65.0	72.7
25	30	180	100	150	240	196.4	133.9	45.9	58.1	64.9
		210			270			53.6	67.7	75.7
28	35	225	115	170	295	246.4	168.0	64.3	81.3	90.9
		270			340			77.1	97.5	109.1
32	40	240	130	195	320	321.6	219.3	78.3	99.1	110.8
		300			380			97.9	123.9	138.5
36	45	290	145	220	380	408.0	278.3	106.5	134.7	150.6
		330			420			121.2	153.3	171.4
40	50	320	160	240	420	504.0	343.7	130.6	165.1	184.6
		360			460			146.9	185.8	207.7

* Note: For shear loads acting towards an edge or where these optimum dimensions are not achievable, please use the simplified strength limit state design process to verify capacity.
 Note: Reduced characteristic ultimate concrete tensile capacity = ϕN_{uc} where $\phi = 0.6$ and N_{uc} = Characteristic ultimate concrete tensile capacity. **For conversion to Working Load Limit MULTIPLY ϕN_{uc} x 0.55
 ***Note: Reduced characteristic ultimate steel tensile capacity = ϕN_{us} where $\phi = 0.8$ and N_{us} = Characteristic ultimate steel tensile capacity. **For conversion to Working Load Limit MULTIPLY ϕN_{us} x 0.56**
 #Note: Design Tensile Capacity ϕN_{ur} = minimum of ϕN_{uc} and ϕN_{us}
DO NOT USE IN WET HOLES

18.2 DESCRIPTION AND PART NUMBERS

Description	Cartridge Size	Part No.
ChemSet™ 801 Cartridge	400 ml	C801C
ChemSet™ 801 Jumbo Cartridge	750 ml	C801J
Mixer Nozzle for 800 Series	-	ISNE

Effective depth, h (mm)

$h \geq 6 * d_h$

(To obtain full steel strength in shear)

Substrate thickness, b_m (mm)

$b_m = \text{greater of: } 1.25 * h, h + (2 * d_h)$

Drilled hole depth, h_1 (mm)

$h_1 = h$
 $h = \text{Effective depth}$

18.3 ENGINEERING PROPERTIES

Typical Engineering Properties of Grade 500 Reinforcing Bar

Rebar Size	10	12	16	20	24	25	28	32	36	40
Drilled Hole Dia, d_h (mm)	14	16	20	25	30	30	35	40	45	50
Stress Area, A_s (mm ²)	78.5	113	201	314	452	491	616	804	1020	1260
Yield Stress, f_y (MPa)	500	500	500	500	500	500	500	500	500	500
Tensile Steel Yield Capacity N_{sy} , (kN)	39.3	56.5	100.5	157.0	226.0	245.5	308.0	402.0	510.0	630.0

For further information refer to reinforcing bar manufacturer's published information and AS/NZS 4671:2001

AVAILABLE IN AUSTRALIA ONLY

STEP 1 Select anchor to be evaluated

Table 1a Indicative combined loading – interaction diagram

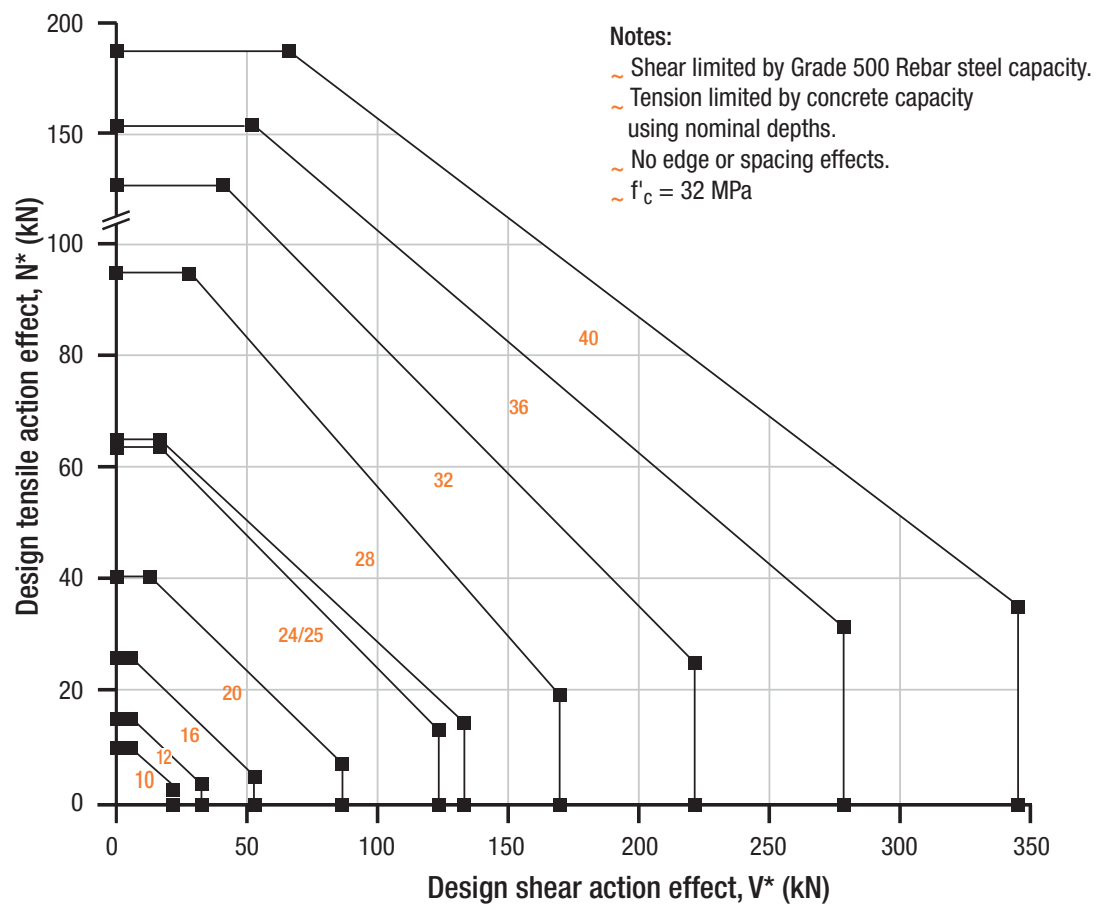


Table 1b Absolute minimum edge distance and anchor spacing values, e_m and a_m (mm)

Anchor size, d_b	10	12	16	20	24	25	28	32	36	40
e_m, a_m	30	36	48	60	72	75	84	96	108	120

Step 1c Calculate anchor effective depth, h (mm)

Refer to nominal recommended effective depths, h, listed in installation and performance details table on page 136.

Effective depth, h (mm)

$h \geq 6 * d_h$

(To obtain full steel strength in shear)

Checkpoint 1 Anchor size determined, absolute minima compliance achieved, effective depth (h) calculated.

AVAILABLE IN AUSTRALIA ONLY

STEP 2 Verify concrete tensile capacity - per anchor

Table 2a Reduced characteristic ultimate concrete tensile capacity, ϕN_{uc} (kN), $\phi_c = 0.6$, $f'_c = 32$ MPa

Anchor size, d_b	10	12	16	20	24	25	28	32	36	40
Drilled Hole Dia, d_h (mm)	14	16	20	25	30	30	35	40	45	50
Effective Depth, h (mm)										
85	11.0									
90	11.6									
95	12.3									
100	12.9	15.5								
105	13.5	16.3								
110	14.2	17.0								
115	14.8	17.8								
125	16.1	19.4	25.8							
140	18.1	21.7	28.9							
150	19.4	23.2	31.0	38.7						
170		26.3	35.1	43.9						
180		27.9	37.2	46.4	55.7	58.1				
210			43.4	54.2	65.0	67.7	75.9			
240			49.5	61.9	74.3	77.4	86.7	99.1		
270				69.7	83.6	87.1	97.5	111.5	125.4	
300				77.4	92.9	96.8	108.4	123.9	139.3	154.8
320				82.6	99.1	103.2	115.6	132.1	148.6	165.1
330					102.2	106.4	119.2	136.2	153.3	170.3
360					111.5	116.1	130.1	148.6	167.2	185.8
420						135.5	151.7	173.4	195.1	216.8
460								189.9	213.7	237.4
500								206.4	232.2	258.0
550									255.5	283.8
600										309.7
625										322.6

Bold values are at ChemSet™ Anchor Stud nominal depths.


Note: Effective depth, h must be $\geq 6 \times$ drilled hole diameter, d_h for anchor to achieve tabled shear capacities. **DO NOT USE IN WET HOLES**

Table 2b Concrete compressive strength effect, tension, X_{nc}

f'_c (MPa)	20	25	32	40	50
X_{nc}	0.79	0.88	1.00	1.12	1.25

Table 2c Edge distance effect, tension, X_{ne}


Anchor size, d_b	10	12	16	20	24	25	28	32	36	40
Edge Distance, e (mm)										
30	0.83									
35	0.91	0.81								
40	1.00	0.88								
50		1.00	0.85							
65			1.00	0.87						
80				1.00	0.88	0.86				
95					1.00	0.97	0.89	0.82		
100						1.00	0.93	0.85		
110							1.00	0.90	0.83	
130								1.00	0.93	0.87
145									1.00	0.93
160										1.00



AVAILABLE IN AUSTRALIA ONLY

Table 2d Anchor spacing effect, end of a row, tension, X_{nae}


For single anchor design, $X_{nae} = 1.0$



Anchor size, d_b	10	12	16	20	24	25	28	32	36	40
Anchor Spacing, a (mm)										
30	0.75									
35	0.79	0.74								
40	0.83	0.78								
50	0.92	0.85	0.76							
60	1.00	0.92	0.81	0.75						
75		1.00	0.89	0.81	0.76	0.75				
95			1.00	0.90	0.83	0.82	0.78			
120				1.00	0.92	0.90	0.86	0.81	0.78	0.75
140					1.00	0.97	0.92	0.86	0.82	0.79
150						1.00	0.95	0.89	0.85	0.81
170							1.00	0.94	0.89	0.85
195								1.00	0.95	0.91
220									1.00	0.96
240										1.00

Table 2e Anchor spacing effect, internal to a row, tension, X_{nai}

For single anchor design, $X_{nai} = 1.0$



Anchor size, d_b	10	12	16	20	24	25	28	32	36	40
Anchor Spacing, a (mm)										
30	0.50									
35	0.58	0.49								
40	0.67	0.56								
50	0.83	0.69	0.52							
60	1.00	0.83	0.63	0.50						
75		1.00	0.78	0.63	0.52	0.50				
95			1.00	0.79	0.66	0.63	0.57	0.49		
120				1.00	0.83	0.80	0.71	0.63	0.56	0.50
150					1.00	1.00	0.89	0.78	0.69	0.63
170							1.00	0.89	0.79	0.71
195								1.00	0.90	0.81
215									1.00	0.90
240										1.00

Checkpoint 2

Design reduced ultimate concrete tensile capacity, ϕN_{urc}

$$\phi N_{urc} = \phi N_{uc} * X_{nc} * X_{ne} * (X_{nae} \text{ or } X_{nai})$$

STEP 3

Verify anchor tensile capacity - per anchor

Table 3a Reduced characteristic ultimate steel tensile capacity, ϕN_{us} (kN), $\phi_n = 0.8$

Anchor size, d_b	10	12	16	20	24	25	28	32	36	40
e_m, a_m	31.4	45.2	80.4	125.6	180.8	196.4	246.4	321.6	408.8	504.0

Step 3b Reduced characteristic ultimate bolt steel tensile capacity, ϕN_{tf} (kN)

Not appropriate for this product.

AVAILABLE IN AUSTRALIA ONLY

Checkpoint **3**

Design reduced ultimate tensile capacity, ϕN_{ur}

$$\phi N_{ur} = \text{minimum of } \phi N_{urc}, \phi N_{us}$$

$$\text{Check } N^* / \phi N_{ur} \leq 1,$$

if not satisfied return to step 1

Tensile performance conversion table

Performance Required	Concrete Tensile Performance		Steel Tensile Performance	
	Notation	Concrete Tension Capacity	Notation	Carbon Steel Tension Capacity
Strength Limit State	ϕN_{urc}	MULTIPLY $\phi N_{urc} \times 1.00$	ϕN_{us}	MULTIPLY $\phi N_{us} \times 1.00$
Working Load Limit	N_{ac}	MULTIPLY $\phi N_{urc} \times 0.55$	N_{as}	MULTIPLY $\phi N_{us} \times 0.56$
Cyclic Loading	N_{yc}	Refer to page 40 for suitable anchor	N_{ys}	Refer to page 40 for suitable anchor
Fire Resistance	$N_{Rk,c,fi,t}$	Refer to pages 238-257	$N_{Rk,s,fi,t}$	Refer to pages 238-257
Cracked Concrete/Tension Zone	$N_{Rd,p}^0$	Refer to pages 258-298	$N_{Rd,s}$	Refer to pages 258-298
Seismic	$N_{Rd,p,sis}^0$	Refer to pages 299-325	$N_{Rd,s,sis}$	Refer to pages 299-325

NOTE: Design Tensile Capacity is the minimum of Concrete Tension and Steel Tension Capacities

STEP **4**

Verify concrete shear capacity - per anchor

Table 4a Reduced characteristic ultimate concrete edge shear capacity, ϕV_{uc} (kN), $\phi_q = 0.6$, $f'_c = 32$ MPa

Anchor size, d_b	10	12	16	20	24	25	28	32	36	40
Edge Distance, e (mm)										
30	2.5									
35	3.2									
40	3.9	4.2								
50	5.5	5.9	6.5							
60	7.2	7.7	8.6	9.6						
75	10.1	10.8	12.0	13.4	14.7	14.7				
95	14.3	15.3	17.1	19.2	21.0	21.0	22.7			
120	20.4	21.8	24.3	27.2	29.8	29.8	32.2	34.4	36.5	38.5
200	43.8	46.8	52.4	58.6	64.1	64.1	69.3	74.1	78.6	82.8
300	80.5	86.1	96.2	107.6	117.8	117.8	127.3	136.1	144.3	152.1
400	123.9	132.5	148.1	165.6	181.4	181.4	196.0	209.5	222.2	234.2
500	173.2	185.2	207.0	231.5	253.6	253.6	273.9	292.8	310.6	327.4
600	227.7	243.4	272.2	304.3	333.3	333.3	360.0	384.9	408.2	430.3


Note: Effective depth, h must be $\geq 6 \times$ drilled hole diameter, d_h for anchor to achieve tabled shear capacities.

Table 4b Concrete compressive strength effect, concrete edge shear, X_{vc}

f'_c (MPa)	20	25	32	40	50
X_{vc}	0.79	0.88	1.00	1.12	1.25

Table 4c Load direction effect, concrete edge shear, X_{vd}

Angle, α°	0	10	20	30	40	50	60	70	80	90 - 180
X_{vd}	1.00	1.04	1.16	1.32	1.50	1.66	1.80	1.91	1.98	2.00



Load direction effect, conc. edge shear, X_{vd}

AVAILABLE IN AUSTRALIA ONLY

Table 4d Anchor spacing effect, concrete edge shear, X_{va}

Note: For single anchor designs, $X_{va} = 1.0$

Edge distance, e (mm)	25	30	35	50	60	75	125	200	300	400	500	600
Anchor spacing, a (mm)												
25	0.70	0.67	0.64	0.60	0.58	0.57	0.54					
30	0.74	0.70	0.67	0.62	0.60	0.58	0.55	0.53				
35	0.78	0.73	0.70	0.64	0.62	0.59	0.56	0.54	0.52			
50	0.90	0.83	0.79	0.70	0.67	0.63	0.58	0.55	0.53	0.53		
60	0.98	0.90	0.84	0.74	0.70	0.66	0.60	0.56	0.54	0.53	0.52	
75	1.00	1.00	0.93	0.80	0.75	0.70	0.62	0.58	0.55	0.54	0.53	0.53
150			1.00	1.00	1.00	0.90	0.74	0.65	0.60	0.58	0.56	0.55
200						1.00	0.82	0.70	0.63	0.60	0.58	0.57
300							0.98	0.80	0.70	0.65	0.62	0.60
400							1.00	0.90	0.77	0.70	0.66	0.63
500								1.00	0.83	0.75	0.70	0.67
625									0.92	0.81	0.75	0.71
750									1.00	0.88	0.80	0.75
875										0.94	0.85	0.79
1000										1.00	0.90	0.83
1250											1.00	0.92
1500												1.00


Table 4e Multiple anchors effect, concrete edge shear, X_{vn}

Note: For single anchor designs, $X_{vn} = 1.0$

Anchor spacing / Edge distance, a / e	0.20	0.40	0.60	0.80	1.00	1.20	1.40	1.60	1.80	2.00	2.25	2.50
Number of anchors, n												
2	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00
3	0.72	0.76	0.80	0.83	0.86	0.88	0.91	0.93	0.95	0.96	0.98	1.00
4	0.57	0.64	0.69	0.74	0.79	0.82	0.86	0.89	0.92	0.94	0.97	1.00
5	0.49	0.57	0.63	0.69	0.74	0.79	0.83	0.87	0.90	0.93	0.97	1.00
6	0.43	0.52	0.59	0.66	0.71	0.77	0.81	0.85	0.89	0.93	0.96	1.00
7	0.39	0.48	0.56	0.63	0.69	0.75	0.80	0.84	0.88	0.92	0.96	1.00
8	0.36	0.46	0.54	0.61	0.68	0.74	0.79	0.84	0.88	0.92	0.96	1.00
9	0.34	0.44	0.52	0.60	0.67	0.73	0.78	0.83	0.87	0.91	0.96	1.00
10	0.32	0.42	0.51	0.59	0.66	0.72	0.77	0.82	0.87	0.91	0.96	1.00
15	0.26	0.37	0.47	0.55	0.63	0.70	0.76	0.81	0.86	0.90	0.95	1.00
20	0.23	0.35	0.45	0.54	0.61	0.68	0.75	0.80	0.85	0.90	0.95	1.00

Table 4f Anchor at a corner effect, concrete edge shear, X_{vs}

Note: For $e_1/e_2 > 1.25$, $X_{vs} = 1.0$

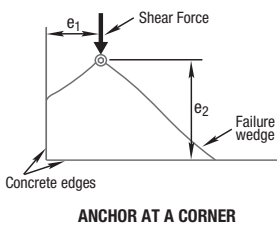

Edge distance, e_2 (mm)	25	30	35	50	60	75	125	200	300	400	600	900
Edge distance, e_1 (mm)												
25	0.86	0.77	0.70	0.58	0.53	0.49	0.41	0.37	0.35	0.34	0.32	0.32
30	0.97	0.86	0.78	0.64	0.58	0.52	0.43	0.38	0.36	0.34	0.33	0.32
35	1.00	0.95	0.86	0.69	0.63	0.56	0.46	0.40	0.37	0.35	0.33	0.32
50	1.00	1.00	1.00	0.86	0.77	0.67	0.52	0.44	0.39	0.37	0.35	0.33
60	1.00	1.00	1.00	0.97	0.86	0.75	0.57	0.47	0.41	0.38	0.36	0.34
75	1.00	1.00	1.00	1.00	1.00	0.86	0.64	0.51	0.44	0.41	0.37	0.35
125	1.00	1.00	1.00	1.00	1.00	1.00	0.86	0.65	0.53	0.48	0.42	0.38
200	1.00	1.00	1.00	1.00	1.00	1.00	1.00	0.86	0.67	0.58	0.49	0.42
300	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00	0.86	0.72	0.58	0.49
400	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00	0.86	0.67	0.55
500	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00	0.77	0.61
600	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00	0.86	0.67
900	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00	1.00	0.86

AVAILABLE IN AUSTRALIA ONLY

Checkpoint 4

Design reduced ultimate concrete edge shear capacity, ϕV_{urc}

$$\phi V_{urc} = \phi V_{uc} * X_{vc} * X_{vd} * X_{va} * X_{vn} * X_{vs}$$

STEP 5

Verify anchor shear capacity - per anchor

Table 5a Reduced characteristic ultimate steel shear capacity, ϕV_{us} (kN), $\phi_v = 0.8$

Anchor size, d_b	10	12	16	20	24	25	28	32	36	40
Grade 500 Rebar	21.4	30.8	54.8	85.7	123.3	133.9	168.0	219.3	278.3	343.7

Step 5b Reduced characteristic ultimate bolt steel shear capacity, ϕV_{sf} (kN)

Not appropriate for this product.

Checkpoint 5

Design reduced ultimate shear capacity, ϕV_{ur}

$$\phi V_{ur} = \text{minimum of } \phi V_{urc}, \phi V_{us}$$

$$\text{Check } V^* / \phi V_{ur} \leq 1,$$

if not satisfied return to step 1

Shear performance conversion table

Performance Required	Concrete Shear Performance		Steel Shear Performance	
	Notation	Concrete Shear Capacity	Notation	Carbon Steel Shear Capacity
Strength Limit State	ϕV_{uc}	MULTIPLY ϕV_{uc} x 1.00	ϕV_{us}	MULTIPLY ϕV_{us} x 1.00
Working Load Limit	V_{ac}	MULTIPLY ϕV_{uc} x 0.55	V_{as}	MULTIPLY ϕV_{us} x 0.45
Cyclic Loading	V_{yc}	Refer to page 40 for suitable anchor	V_{ys}	Refer to page 40 for suitable anchor
Fire Resistance	$V_{Rk,c,fi,t}$	Refer to pages 238-257	$V_{Rk,s,fi,t}$	Refer to pages 238-257
Cracked Concrete/Tension Zone	$V_{Rd,c}^0$	Refer to pages 258-298	$V_{Rd,s}^0$	Refer to pages 258-298
Seismic	$V_{Rd,c,sls}^0$	Refer to pages 299-325	$V_{Rd,s,sls}^0$	Refer to pages 299-325

NOTE: Design Shear Capacity is the minimum of Concrete Shear and Steel Shear Capacities

STEP 6

Combined loading and specification

Checkpoint 6

Check

$$N^* / \phi N_{ur} + V^* / \phi V_{ur} \leq 1.2,$$

if not satisfied return to step 1

Specify – Reinforcing Bar Anchorage

Ramset™ ChemSet™ 801 with (Anchor Size) grade 500 Rebar.
Drilled hole depth to be (h) mm.

Example

Ramset™ ChemSet™ 801 with
N20 grade 500 Rebar
Drilled hole depth to be 160 mm.
To be installed in accordance with
Ramset™ Technical Data Sheet.